

Butterfly hysteresis loop and dissipative spin reversal in the $S=1/2$, V_{15} molecular complex

I. Chiorescu^a, W. Wernsdorfer^a, A. Müller^b, H. Bögge^b and B. Barbara^a.

^a *Laboratoire de Magnétisme Louis Néel, CNRS, BP 166, 38042-Grenoble, France.*

^b *Fakultät für Chemie, Universität Bielefeld, D-33501 Bielefeld, Germany.*

(February 1, 2008)

Time resolved magnetization measurements have been performed on a spin $1/2$ molecular complex, so called V_{15} . Despite the absence of a barrier, magnetic hysteresis is observed over a timescale of several seconds. A detailed analysis in terms of a dissipative two level model is given, in which fluctuations and splittings are of same energy. Spin-phonon coupling leads to long relaxation times and to a particular "butterfly" hysteresis loop.

PACS numbers: 75.50.Xx, 75.45.+j, 71.70.-d

In this letter we study the dynamics of the magnetization reversal of a molecular crystal made of nanometric molecules with non-interacting $S = 1/2$ spins. Despite the absence of energy barrier against spin reversal, this system shows hysteresis. This result are interpreted in details assuming spin rotation in a phonon bath, which is different from the situation of large spin molecules where only the spin bath is believed to be relevant [1–4]. Resonant phonon transitions are irrelevant, unless between states at different energies [5] or in the presence of a transverse field large enough to create a tunnel splitting of the order of the temperature energy scale [6].

The molecular complex $K_6[V_{15}^{IV}As_6O_{42}(H_2O)] \cdot 8H_2O$ (so-called V_{15}) [7] is made of molecules with fifteen V^{IV} ions of spin $S = 1/2$, placed in a quasi-spherical layered structure formed of a triangle, sandwiched by two hexagons. The symmetry is trigonal (space group $R\bar{3}c$, $a = 14.029$ Å, $\alpha = 79.26^\circ$, $V = 2632$ Å³). The unit-cell contains two V_{15} clusters and it is large enough that dipolar interactions between different molecules are negligible (a few mK). All intra-molecular exchange interactions being antiferromagnetic, the total spin of this molecule is $S = 1/2$. Such a small spin has zero energy barrier and relatively large splitting in zero applied field ($\sim 10^{-2}$ K). Although spin entanglement results in 2^{15} eigenstates per molecule, the magnetization curves will be interpreted in terms of a dissipative two level model [8–10].

Time-resolved magnetization measurements were performed with the micro-SQUID technique (50 – 400 mK, 0 – 0.7 T/s) [11]. In order to maximize thermal contact with the bath, we choose a sample holder made by greece and silver powder and a small crystal of the V_{15} (~ 50 μm). As an example we give a few hysteresis loops in Fig. 1a and Fig. 2a (only the positive parts are represented, the other ones being rigorously symmetrical).

When the field increases, coming from the negative saturation, the magnetization curve passes through the origin of the coordinates, reaches a plateau and then approaches saturation. This leads to a winged hysteresis loop characterized by the absence of irreversibility near zero field. Nevertheless, the initial susceptibilities being larger the faster sweeping field, the magnetization is out of equilibrium also near zero field where it appears to be reversible.

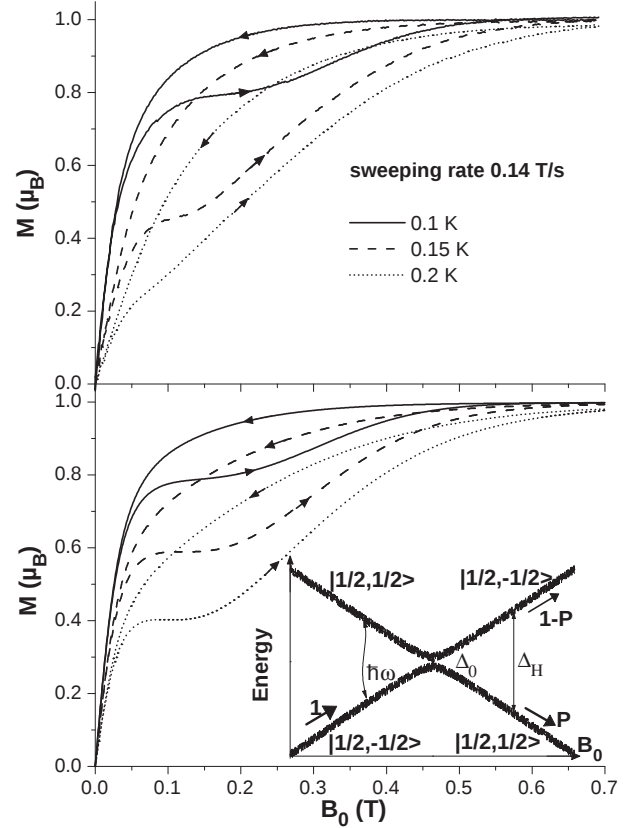


FIG. 1. Measured (a–top) and calculated (b–bottom) butterfly hysteresis loops for three temperatures and for a given field sweeping rate 0.14 T/s. The plateau is more pronounced at low T . The inset is a schematic representation of a two-level system $S_Z = \pm 1/2$ with repulsion due to non-diagonal matrix elements. In a swept field the switching probability P is given by the Landau-Zener formulae (see text). The two levels are broadened by the hyperfine fields and the absorption or the emission of phonons can switch the polarization state of spins.

The wings depend sensitively on temperature T and field sweeping rate r . In Fig. 1a, where three hysteresis

loops are presented at three different temperatures for a given sweeping rate, the plateau is higher and more pronounced at low temperature. The same tendency is observed at a given temperature and faster sweeping rates (Fig. 2a). When compared to its equilibrium limit (dotted curve in Fig. 2), each magnetization curve shows a striking feature: the plateau intersects the equilibrium curve and the magnetization becomes smaller than at equilibrium. Equilibrium is then reached in higher fields near saturation.

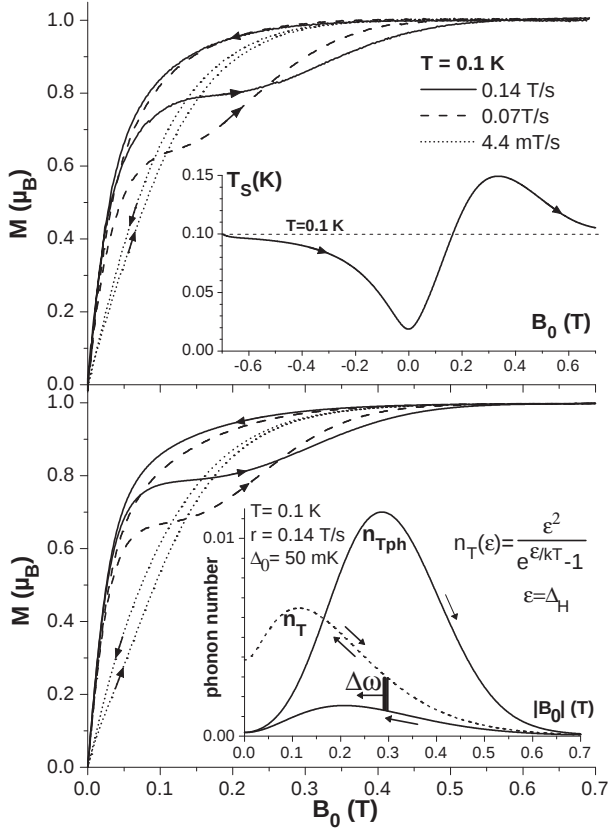


FIG. 2. Measured (a—top) and calculated (b—bottom) hysteresis loops for three field sweeping rates at $T = 0.1$ K. The observed plateau is more pronounced at high sweeping rate. The equilibrium curve can be approximated by the median of the two branches of the low sweeping rate hysteresis loop (dotted curve). In the top inset is plotted the spin and phonon temperature $T_S = T_{ph}$ for $T = 0.1$ K and $r = 0.14$ T/s, when the field is swept from negative values. T_S decreases until zero-field and then increases linearly within the plateau region. Then it overpasses the bath temperature to finally reach the equilibrium. In the bottom inset the calculated number of phonons with $\hbar\omega = \Delta_H$ is plotted vs. the sweeping field modulus (note the arrows) at equilibrium ($T_{ph} = T_S = T$, dashed line) and out-of-equilibrium ($n_{T_{ph}} = n_{T=T_S}$, $r = 0.14$ T/s, black line). The difference between the two curves (thick segment $\Delta\omega$) suggests the moving hole in the phonon distribution, while their intersection gives the plateau intercept of the equilibrium magnetization curve.

In order to interpret this magnetic behavior of the

V_{15} molecules, we will analyse how the level occupation numbers vary in this two level system (see Fig. 1b inset) when sweeping an external field. In the absence of dissipation, a 2-level model is well described by the bare Landau-Zener model, in the adiabatic or non-adiabatic case (low or high sweeping rates). The probability for the $|1/2, -1/2\rangle \leftrightarrow |1/2, 1/2\rangle$ transition is $P = 1 - \exp(-\pi\Delta_0^2/4\hbar\mu_B r)$. In such a Landau-Zener transition, the plateaus of Fig. 2 should decrease if the sweeping rate increases, which is contrary to the experiments. Taking the typical value $r = 0.1$ T/s and the zero-field splitting $\Delta_0 \cong 0.05$ K [12–15], one gets a ground state switching probability very close to unity: in the absence of dissipation the spin 1/2 must adiabatically follow the field changes. Extremely large sweeping rates ($\approx 10^9$ T/s) would be needed to get into the quantum non-adiabatic regime $P < 1$. The mark of the V_{15} system is that the dissipative spin-phonon coupling is acting also near zero applied field because $\hbar\omega \approx \Delta_0$ is of the order of the bath temperature, which is not the case for large spin molecules where $\Delta_0 \ll k_B T$. The spin temperature T_S is such that $n_1/n_2 = \exp(\Delta_H/k_B T_S)$, where $\Delta_H = \sqrt{\Delta_0^2 + (2\mu_B B_0)^2}$ is the two levels field-dependent separation, and $n_{1,2}(n_{1,2eq})$ the out of equilibrium (equilibrium) level occupation numbers. In the magnetization curves at 0.1 K (Fig. 1,2a), the spin temperature is significantly lower than the bath temperature T ($n_1 > n_{1eq}$, $T_S < T$) between -0.3 T (when the magnetization curve departs from the equilibrium one) and 0.15 T (the field at which the magnetization curve intersects the equilibrium one). After this intercept T_S is larger than the bath temperature ($n_1 < n_{1eq}$, $T_S > T$), and at sufficiently high fields (about 0.5 T) it reaches the equilibrium value ($n_1 = n_{1eq}$, $T_S = T$).

In a direct process, the spins at the temperature T_S should relax to the phonons temperature within a timescale τ_1 , the phonons being at the bath temperature. However, even with a silver sample holder, it is not possible to maintain the phonon temperature equal to the temperature of the bath. This is because in V_{15} below 0.5 K, the heat capacity of the phonons C_{ph} is very much smaller than that of the spins C_S , so that the energy exchanged between spins and phonons will very rapidly adjust the phonons temperature T_{ph} to the spin one T_S . Furthermore, the energy is transferred from the spins only to those phonon modes with $\hbar\omega = \Delta_H$ (within the resonance line width). The number of such lattice modes being much smaller than the number of spins, energy transfer between the phonons and the sample holder must be very difficult, a phenomenon known as the phonon bottleneck [16]. Following [17], the number of phonons per molecule available for such resonant transitions is $n_T = \int_{\Delta\omega} \sigma(\omega) d\omega / (\exp(\hbar\omega/kT) - 1)$, where $\sigma(\omega) d\omega = 3V\omega^2 d\omega / (2\pi^2 v^3)$ = number of phonon modes between ω and $\omega + d\omega$ per molecule of volume V , v is the phonon velocity and $\Delta\omega$ is the transition linewidth due to fast hyperfine field fluctuations (they broaden both en-

ergy levels) [18]. Taking the typical values $v \approx 3000$ m/s, $T \approx 10^{-1}$ K and $\Delta\omega \approx 5 \cdot 10^2$ MHz we find n_T of the order of $\approx 10^{-6}$ to 10^{-8} phonons/molecule. Such a small number of phonons is very rapidly absorbed, burning a hole of width $\Delta\omega$ in the phonon density of states at the energy $\hbar\omega = \Delta_H$ [16]. If this phonon density of states does not equilibrate fast enough, the hole must persist and move with the sweeping field, leading to a phonon bottleneck.

Now this description will be made quantitative. For a given splitting Δ_H , the time evolution of the two levels populations $n_{1,2}$ and of the phonon numbers $n_{T_{ph}}$ at T_{ph} obeys the set of two differential equations [17]: (i) $-\dot{n}_1 = \dot{n}_2 = P_{12}n_1 - P_{21}n_2$ and (ii) $\dot{n}_{T_{ph}} = -(n_{T_{ph}} - n_T)/\tau_{ph} - P_{12}n_1 + P_{21}n_2$, where $P_{12,21}$ are the transition probabilities between the two levels (they are themselves linear functions of $n_{T_{ph}}$) and $\tau_{ph} \approx L/2v$ is the phonon-bath relaxation time (L is the sample size). Using the notations $x = (n_1 - n_2)/(n_{1eq} - n_{2eq})$, $y = (n_{T_{ph}} - n_T)/(n_T + n/2)$ with $n = \int_{\Delta\omega} \sigma(\omega)d\omega$ we get: (i) $\dot{x} = (1 - x - xy)/\tau_1$ and (ii) $\dot{y} = -y/\tau_{ph} + bx$, where $b = C_S/C_{ph}$ and $1/\tau_1 = P_{12} + P_{21}$ the direct spin-phonon relaxation time. By solving numerically this system for typical values, e.g. $\tau_1 = 10^{-2}$ s, $\tau_{ph} < 10^{-6}$ s, $b > 10^5$, we can see that $T_{ph} \rightarrow T_S \neq T$ (phonon bottleneck) very rapidly, as expected. This leads to $y = 1/x - 1$ and the second equation of the differential system becomes $\dot{x} = (x - x^2)/(1 + bx^2)/\tau_{ph}$. In the limit $b \gg 1$ (in our case $b \approx 10^8 - 10^{10}$) this equation has the solution:

$$-t/b\tau_{ph} = x - x_0 + \ln((x - 1)/(x_0 - 1)), \quad (0.1)$$

where $x_0 = x(t = 0)$ and $b\tau_{ph}$ is the spin-phonon recovery relaxation time ($T_{ph} = T_S \rightarrow T$). When the system is not far from equilibrium ($x \sim 1$), we get an exponential decay of the magnetization, with the same time constant $\tau_H = b\tau_{ph}$. For a spin 1/2 system [17]:

$$\tau_H = \alpha \frac{\tanh^2(\Delta_H/2k_B T)}{\Delta_H^2}, \quad (0.2)$$

with $\alpha = 2\pi^2 \hbar^2 v^3 N \tau_{ph} / 3\Delta\omega$ (N the molecule density).

The dynamical magnetization curves calculated in this model are given Fig. 1b and Fig. 2b. We started from equilibrium ($x_0 = 1$) in large negative fields. Then we let the system relax for a very short time δt and we calculated $x(\delta t)$ using Eq. 0.1. This value was taken as the initial value for the next field (the field step is $r\delta t$). The parameters have been chosen to mimic the measured curves of Fig. 1a and Fig. 2a [19]. The obtained similarity supports the possibility of the phonon bottleneck effect at the timescale of a few 0.1 s. In the Fig. 2a inset, we show the variation of the calculated spin-phonon temperature T_S for $T = 0.1$ K and $r = 0.14$ T/s. We can note a linear variation in the plateau region (small positive fields, $n_1/n_2 \approx cst.$), after a cooling in negative fields. The slope of this quasi-adiabatic linear region varies with the bath temperature and sweeping rate and

gives the plateau dependence on these two parameters (see Figs. 1, 2).

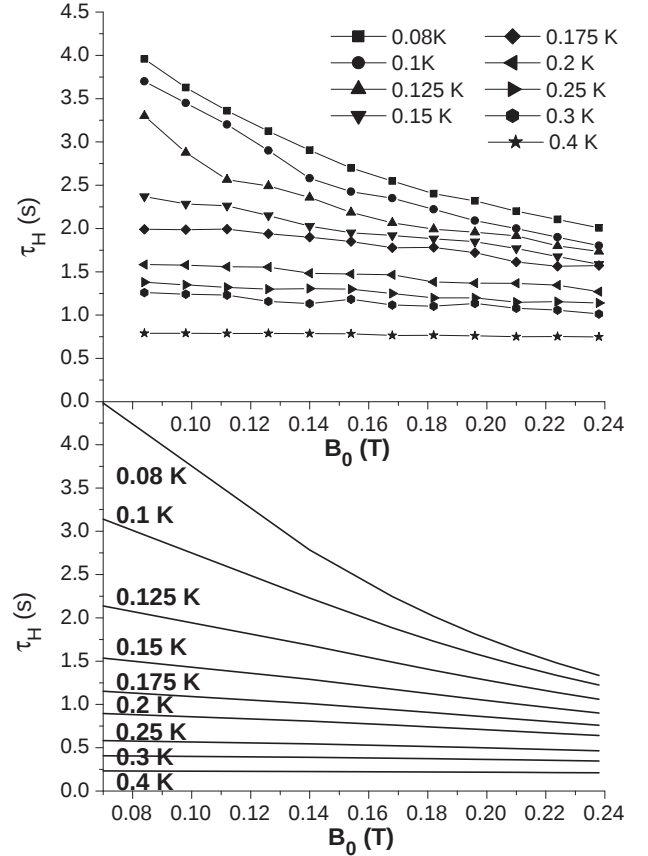


FIG. 3. The relaxation times τ_H , measured (a-top) and calculated (b-bottom, same parameters as in Fig. 1, 2b).

In the Fig. 2b inset we show the calculated field evolution of the number of phonons at energy $\hbar\omega = \Delta_H$ at equilibrium ($T_{ph} = T_S = T$, dashed line) and out-of-equilibrium ($n_{T_{ph}} = n_{T=T_S}$, $r = 0.14$ T/s, black line). The difference between the two curves (thick segment $\Delta\omega$) suggests the moving hole in the phonon distribution, while their intersection gives the plateau intercept of the equilibrium magnetization curve (above which the hole disappears and $T_{ph} = T_S > T$). Let note that in zero field the system is out-of-equilibrium even if magnetization passes through the origin of coordinates (without a barrier, the switch between $+1/2$ and $-1/2$ follows the level structure shown Fig. 1 inset). At larger fields, in the plateau region, $n_1/n_2 \approx cst.$ at timescales shorter than $\tau_H = b\tau_{ph}$ (Eq. 0.2), even after the plateau crosses the equilibrium curve. Equilibrium is reached when τ_H becomes small enough.

Furthermore, we measured the relaxation of the magnetization of our crystal at different fields and temperatures, along the plateau region. The relaxation curves compared well to exponential decay and the obtained relaxation times are presented in Fig. 3a. The comparison with those calculated (Fig. 3b) is acceptable. But we

noted that a direct fit to Eq. 0.1 would necessitate larger values for α and Δ_0 ($\approx 0.4 - 0.6$ sK² and $\approx 0.2 - 0.3$ K). Note that in V₁₅ we have $b\tau_{ph} > \tau_1$ and this leads to the phonon bottle-neck regime. However, in other systems one might have $b\tau_{ph} < \tau_1$ in which case the phonons would be at equilibrium but still with a butterfly hysteresis loop (τ_H is a linear combination of τ_1 and $b\tau_{ph}$ [17]). This type of hysteresis loop is general and characterizes dissipative spin reversal in the absence of barrier.

In conclusion, the V₁₅ molecular complex constitutes an example of dissipative two-levels system [8] of mesoscopic size. The total spin 1/2 being formed of a large number of interacting spins, its splitting results from the structure itself of the molecule (intra-molecular hyperfine and Dzyaloshinsky-Moriya couplings) and it is rather large (a fraction of Kelvin) [12]. In V₁₅ and in other low-spin systems, splittings must be much larger than in large-spin molecules where the presence of energy barriers lowers them by orders of magnitude (e.g. 10^{-11} K in Mn₁₂ [1,2]). This is the reason why spin-phonon transitions within the tunneling gap are important in low-spin molecules and not relevant in high-spin ones, unless a large transverse field is applied [6] (it increases the tunnel splitting and probability) in which case we would also expect similar phenomena.

ACKNOWLEDGMENTS

We are very pleased to thank P.C.E. Stamp, S. Miyashita, I. Tupitsyn, A. K. Zvezdin, V. Dobrovitski, H. De Raedt and A. J. Leggett for useful discussions and E. Krickemeyer, P. Kögerler, D. Mailly, C. Paulsen and J. Voiron for on-going collaborations.

corresponding author: ichiores@polycnrs-gre.fr

-
- [1] L. Thomas, F. Lioni, R. Ballou, D. Gatteschi, R. Sessoli, B. Barbara, Nature, **383**, **145**, (1996). J. R. Friedman, M. P. Sarachik, J. Tejada, R. Ziolo, Phys. Rev. Lett., **76**, 3830, (1996). For a recent review see: B. Barbara, L. Thomas, F. Lioni, I. Chiorescu, A. Sulpice, J. Magn. Magn. Mat., **200**, 167, (1999).
 - [2] B. Barbara and L. Gunther, Physics World, **12**, 35, (1999). I. Tupitsyn and B. Barbara, to be published.
 - [3] *Quantum Tunneling of Magnetization - QTM '94*, NATO ASI, edited by L. Gunther & B. Barbara, Series E **301**, (Kluwer Publishing, 1995): A. Garg, 273 and N. V. Prokof'ev, P.C.E. Stamp, 347.
 - [4] N. V. Prokof'ev and P.C.E. Stamp, Phys. Rev. Lett., **80**, 5794, (1998). *Tunneling in Complex Systems*, Proc. Inst. for Nuclear Theory, vol.5, edited by S. Tomsovic, (World Scientific, 1998): P.C.E. Stamp, 101-197. G. Rose and P.C.E. Stamp, cond-mat/9810350.
 - [5] F. Hartmann-Boutron, P. Politi and J. Villain, Int. J. Mod. Phys. B, **10**, 2577, (1996); M. Leuenberger, D. Loss, EuroPhys. Letters, **46**, 5, 692, (1999) and cond-mat/9907154.
 - [6] G. Belessa, N. Vernier, B. Barbara, D. Gatteschi, Phys. Rev. Lett., **83**, 2, 416, (1999).
 - [7] A. Müller, J. Döring, Angew. Chem. Int. Ed. Engl., **27**, 1721, (1991). D. Gatteschi, L. Pardi, A. L. Barra, A. Müller, Molecular Engineering, **3**, 157-169, (1993). D. Gatteschi, L. Pardi, A. L. Barra, A. Müller, J. Döring, Nature, **354**, 465, (1991).
 - [8] A. J. Leggett, S. Chakravarty, A. T. Dorsey, M. P. A. Fisher, A. Garg, W. Zwerger, Rev. Mod. Phys. **59**, 1, (1987). M. Grifoni, Peter Hänggi, Phys.Rep., **304**, 5-6, (oct. 1998).
 - [9] C. Zener, Proc. R. Soc. London, Ser. **A137**, 696, (1932). L.D. Landau, Phys. Z. Sowjetunion, **2**, 46, (1932).
 - [10] H. De Raedt, S. Miyashita, K. Saito, D. Garcia-Pablos, N. Garcia, Phys. Rev. B, **56**, 18, 11761, (1997). S. Miyashita, J. Phys. Soc. Jpn., **64**, 3207-3214, (1995). Y. Kayanuma, H. Nakayama, Phys. Rev. B, **57** (20), 13099, (1998). E. Shimshoni, A. Stern, Phys. Rev. B, **47**, 9523, (1993).
 - [11] W. Wernsdorfer, E. Bonet Orozco, K. Hasselbach, A. Benoit, D. Mailly, O. Kubo, H. Nakano and B. Barbara, Phys. Rev. Lett., **79**, 4014, (1997). W. Wernsdorfer et al., cond-mat/9912123.
 - [12] For an isolated Kramers spin 1/2, $\Delta_0 = 0$. However, the total spin 1/2 of V₁₅ comes from 15 coupled spins and different intra-molecular couplings such as hyperfine ($\vec{A}\vec{I} \cdot \vec{S}, I = 7/2, A \approx 10$ mK [15]) and Dzyaloshinsky-Moriya interactions [13,14] could generate a splitting. In particular, the two $S = 1/2$ low-lying degenerate doublets and the $S = 3/2$ first excited quartet could be slightly mixed by D-M interactions, removing the degeneracy of the $S = 1/2$ doublet. A value $\Delta_0 \approx 50$ mK is strongly supported by the experiment-to-model comparison in Figs. 1 and 2.
 - [13] M. I. Katsnelson, V. V. Dobrovitski, B. N. Harmon, Phys. Rev. B, **59**, 6919 (1999), cond-mat/9906375.
 - [14] B. Barbara, L. Thomas, F. Lioni, A. Sulpice, A. Caneschi, J. Magn. Magn. Mat., **177-181**, 1324, (1998).
 - [15] G. C. Carter, L. H. Bennett, D. J. Kahan, Metallic Shifts in NMR, Progr. in Mat. Sc, **20**, part I, 364, Pergamon Press Ltd., (1977).
 - [16] J. H. Van Vleck, Phys. Rev., **59**, 724, (1941). K. W. H. Stevens, Rep. Prog. Phys., **30**, 189, (1967).
 - [17] A. Abragam, B. Bleaney, Electronic Paramagnetic Resonance of Transition Ions, Clarendon Press - Oxford, chap. 10, (1970).
 - [18] The fast hyperfine fluctuations are characterized by the transvers nuclear relaxation time T_2 associated with the dipolar internuclear interactions and the total spread of the energy is given by hyperfine couplings [4].
 - [19] $\alpha = 0.15$ sK² ($2.9 \cdot 10^{-47}$ sJ²), $\Delta_0 = 50$ mK within a precision range of $\approx 20\%$. Taking $L \sim 30 - 50$ μm , $N \sim 10^{27}$ m⁻³, $\Delta\omega \sim 5 \cdot 10^8$ s⁻¹, one gets a phonon velocity $v \approx 2800 - 3600$ m/s which is quite a reasonable value.